

Effect of fluctuations on vortex lattice structural transitions in superconductors

A. Gurevich

Applied Superconductivity Center University of Wisconsin, Madison, Wisconsin 53706

V.G. Kogan

Ames National Laboratory and Department of Physics and Astronomy, Iowa State University, Ames Iowa 50011
(February 1, 2008)

The rhombic-to-square transition field $H_{\square}(T)$ for cubic and tetragonal materials in fields along [001] is evaluated using the nonlocal London theory with account of thermal vortex fluctuations. Unlike extended Ginzburg-Landau models, our approach shows that the line $H_{\square}(T)$ and the upper critical field $H_{c2}(T)$ do not cross due to strong fluctuations near $H_{c2}(T)$ which suppress the square anisotropy induced by the nonlocality. In increasing fields, this causes re-entrance of the rhombic structure in agreement with recent neutron scattering data on borocarbides.

PACS numbers: **74.60.-w, 74.60.Ge, 74.70.Dd**

Complex behavior of vortex lattices (VLs) even in cubic superconductors like Nb has been known for a long time [1]. Recent progress in understanding the evolution of VLs with the magnetic field H and temperature T became possible due to availability of large high quality crystals of borocarbides [2], which triggered a score of small-angle neutron scattering (SANS) [3–5], scanning tunneling [6,7], and decoration experiments [8]. Of a particular interest is the ubiquitous structural transition between rhombic and square VLs in increasing fields along the c axis of tetragonal borocarbides [3–5].

For this case, the vortex repulsion is *isotropic* within the standard London and Ginzburg-Landau (GL) theories, so that vortices should always form the hexagonal Abrikosov lattice, which provides the maximum vortex spacing for a given flux density B/ϕ_0 (ϕ_0 is the flux quantum). There is no coupling between the VL and the crystal in these models; as a consequence, the VL orientation is arbitrary and no VL structural transitions are expected. A full microscopic theory of the mixed state contains this coupling, but involves self-consistent calculations of the gap and current distributions, a formidable task even for materials with the GL parameter $\kappa \sim 1$ [9]. The situation simplifies in high- κ materials (like borocarbides), for which one can utilize a more transparent nonlocal London model [10]. Within this approach, the VL coupling to the crystal is provided by the basic nonlocal relation between the current density and the vector potential, $J_{\alpha}(\mathbf{r}) = \int Q_{\alpha\beta}(\mathbf{r} - \mathbf{r}') A_{\beta}(\mathbf{r}') d^3\mathbf{r}'$, where the kernel Q depends on the Fermi surface [10,11], the pairing symmetry [12], and the field orientation. Here, we consider cubic or tetragonal s-wave materials in fields along the c axis so that $Q(\mathbf{r})$ has the square symmetry.

The kernel $Q(r)$ decays over the nonlocality range $\rho = f(T, \ell)\xi_0$, where ℓ is the mean-free path for non-magnetic scatterers and ξ_0 is the BCS zero- T coherence length. The function f decreases slowly with T and is suppressed strongly by scattering [10,11]. The nonlocal-

ity adds to the intervortex interaction a short-range potential $V(x, y)$ with the symmetry of the crystal. In the low field limit, V is irrelevant and the VL is triangular; still, V removes the orientational degeneracy and locks the VL onto certain crystal direction. With decreasing intervortex spacing $a(B)$, the potential V drives the triangular VL into a square at a field $H_{\square}(T)$. The transition curve $H_{\square}(T)$ is the subject of this work.

The nonlocal London model describes correctly the observed structure and orientation of rhombic VLs in small fields [5] and the structural evolution toward the square [8]. Moreover, the fast increase of $H_{\square}$ with increasing impurity concentration predicted by the model has been verified by SANS [13]. Still, there is an open question on what happens when the applied field $H > H_{\square}$ keeps increasing. The nonlocal London model per se implies that the square VL should persist all the way up to H_{c2} since the shorter the intervortex distance, the stronger the role of the square-symmetric potential V . This conjecture is supported by calculations based on the GL theory extended to include the 4th order gradient terms [6,14,15]; the model predicts that the lines $H_{\square}(T)$ and $H_{c2}(T)$ should cross as sketched in the inset to Fig. 1.

However, recent SANS data for $\text{LuNi}_2\text{B}_2\text{C}$ [16] indicate that instead of crossing $H_{c2}(T)$, the line $H_{\square}(T)$ curves up to avoid H_{c2} and becomes two-valued, see Fig. 1. The upper branch of $H_{\square}(T)$ marks the re-entrant transition of the rhombic VL in increasing fields, which then evolves toward the triangular VL as $H \rightarrow H_{c2}$. In this Letter we argue that vortex fluctuations combined with nonlocal effects can account for this unexpected behavior.

Below we evaluate the mean-squared amplitude $\overline{u^2}$ of thermal vortex fluctuations using the elastic energy of the deformed VL. Unlike the case of *isotropic* superconductors, an important role in this energy is played by VL *rotations* relative to the crystal. We show that $\overline{u^2}$ remains finite at the transition line $H_{\square}(T)$, but diverges as B approaches $H_{c2}(T)$. In the vicinity of $H_{c2}(T)$, the

anisotropic nonlocal potential $V(x, y)$ is averaged out by fluctuations, and the interaction becomes isotropic. As a result, the rhombic VL becomes preferable, turning into the hexagonal Abrikosov VL as $B \rightarrow H_{c2}$. The re-entrance of the rhombic VL in increasing fields occurs if $\overline{u^2} \sim \xi_0^2$, i.e., the amplitude of fluctuations needed to wash out the nonlocal effects is much smaller than that required for the VL melting. This re-entrance, therefore, can happen in nearly cubic materials, in which vortices are not split into “pancakes” and fluctuations are weak. We evaluate the shape of the $H_{\square}(T)$ curve using model parameters of $\text{LuNi}_2\text{B}_2\text{C}$ for which in the clean limit $\rho(T) \simeq (1 \div 2)\xi_0$ [11,17]. We reproduce the shape of this curve seen in the SANS data [16].

Let us consider the equilibrium square VL with diagonals along [100] and [010] directions, which we take as x and y axes. We are interested mainly in the high field region, where the VL can be considered as incompressible [18]. Then the displacement of vortices $u_i(x, y; z)$ ($i = x, y$) satisfy $\text{div} \mathbf{u} = \partial_x u_x + \partial_y u_y = 0$ and the symmetric strain tensor $u_{ij} = (\partial_j u_i + \partial_i u_j)/2$ has only two independent components: u_{xx} and u_{xy} . Since the VL orientation is locked on the crystal, rotations of VL about [001], $\omega_{xy} = (\partial_x u_y - \partial_y u_x)/2$, cause an energy increase. Then the energy density U of the deformed VL reads [19]:

$$2U = c_s u_{xx}^2 + c_x u_{xy}^2 + c_\omega \omega_{xy}^2 + c_{44} (\partial_z \mathbf{u})^2. \quad (1)$$

Our notation is motivated by the following. A uniform displacement $u_x = \epsilon x$, $u_y = -\epsilon y$ ($\epsilon \ll 1$ is a constant) is of a special interest: it is this deformation that transforms the square above $H_{\square}$ into a rhombus for $B < H_{\square}$. This deformation was named “squash” [20], so that c_s is the squash modulus. Since this is a second order phase transition, c_s must vanish at $B = H_{\square}$. Further, the “simple” x -directed shear is $u_x = \epsilon y$, $u_y = 0$ so that only $u_{xy} \neq 0$; thus the notation c_x for this shear mode. The shear energy depends on the shear direction, but the corresponding moduli can all be expressed in terms of c_x and c_ω [19]. We take all moduli in Eq. (1) except the tilt c_{44} as practically nondispersive [18].

Next, we calculate the mean-squared vortex displacement $\overline{u^2}(T, B) = \overline{u_x^2} + \overline{u_y^2}$. Writing the total elastic energy in the Fourier space and utilizing the equipartition theorem, we obtain [21]:

$$\overline{u^2} = \int \frac{q dq dk_z d\phi}{(2\pi)^3} \frac{2T}{q^2 c(\phi)/4 + c_{44}(k_z, q) k_z^2}, \quad (2)$$

where $k_x = q \cos \phi$, $k_y = q \sin \phi$, and $c(\phi) = c_\omega + c_x \sin^2 2\phi + c_s \cos^2 2\phi$. With the large fields tilt modulus $c_{44}(k) = c_{44}(0)/(1 + \lambda^2 k^2)$, integration over k_z and q gives $\overline{u^2} = \overline{u_0^2} \eta$. Here $\overline{u_0^2} \sim T \lambda / a^2 \sqrt{c_x c_{44}(0)}$ is the mean-squared displacement for the triangular VL with $c_{66} = c_x$ and $c_{44}(0) = B^2/8\pi$ [22,18]. Taking $\overline{u_0^2}$ for a hexagonal VL in a uniaxial material for $\mathbf{B} \parallel c$ [18], we arrive at

$$\overline{u^2} = 16\sqrt{2}\pi^2 \lambda_a \lambda_c \xi_a T \eta / \phi_0^2 s(b), \quad (3)$$

$$s^2 = b(1-b)^3 \ln(2 + 1/\sqrt{2b}). \quad (4)$$

Here, $\lambda_{a,c}$ are penetration depths, $b = B/H_{c2}$, and

$$\eta = \frac{2\sqrt{c_x}}{\pi} \int_0^\pi \frac{d\phi}{\sqrt{c(\phi)}} = \frac{4}{\pi} \sqrt{\frac{c_x}{c_x + c_\omega}} \mathbf{K}\left(\frac{c_x - c_s}{c_\omega + c_x}\right), \quad (5)$$

where $\mathbf{K}(m)$ is a complete elliptic integral.

As follows from Eqs. (3)-(5), $\overline{u^2}(T, B)$ remains *finite* at the instability point $c_s = 0$. Thus, vortex fluctuations do not affect the mean-field character of the second order transition at $H_{\square}$. This unusual behavior occurs because the rotational modulus c_ω is *finite*, otherwise $\overline{u^2}$ would diverge logarithmically as $B \rightarrow H_{\square}$.

The moduli c_x and c_ω in intermediate fields, $H_{c1} \ll B \ll H_{c2}$, are estimated as $c_x \simeq \phi_0 B / (8\pi\lambda)^2$ and $c_\omega \simeq \rho^2 B^2 / 2\pi\lambda^2 \sqrt{b}$ [23]. For $c_\omega/c_x \sim \rho^2/a\xi \ll 1$, we obtain $\eta \simeq (2/\pi) \ln(16c_x/c_\omega)$. Hence, the nonlocality affects $\overline{u^2}$ via the weakly-varying factor $\eta \sim \ln(\xi/\rho b^{1/4})$, i.e., $\overline{u^2}(T, B)$ is insensitive to detailed behavior of $c_\omega(T, B)$ and $c_x(T, B)$. Since $\overline{u^2} \propto (H_{c2} - B)^{-3/2}$ diverges only at H_{c2} , the fluctuations suppress the weak VL-crystal coupling mainly near H_{c2} .

We now turn to evaluation of the curve $H_{\square}(T)$. The free energy F of fluctuating VL can be written as:

$$F = \frac{B^2}{8\pi} \sum_G \frac{e^{-(C\xi^2 + \overline{u^2})G^2/2}}{1 + \lambda^2 G^2 + \rho^2 \lambda^2 G_x^2 G_y^2}. \quad (6)$$

Here the sum runs over $G_x = \pi\sqrt{2}(m-n)/a \tan^{1/2}(\beta/2)$, $G_y = \pi\sqrt{2}(m+n) \tan^{1/2}(\beta/2)/a$, which form the reciprocal lattice; β is the apex angle of the rhombic cell, and m, n are integers. The last term in the denominator describes the nonlocal correction to the London theory [10,14]. The factor $\exp(-C\xi^2 G^2/2)$ accounts for the finite size of the vortex core [18], which provides a cutoff in the London model. The B dependent quantity C was estimated theoretically as $0.5 < C < 4$ [24]. By and large, the data on the field dependence of SANS form-factors are consistent with $C \simeq 1$ [25], the value we adopt below.

Fluctuations enter the energy (6) via the Debye-Waller factor $\exp(-\overline{u^2} G^2/2)$, which accounts for the thermal smearing of the vibrating VL [22]. For $\overline{u^2} > \rho^2$, the fluctuations wash out the nonlocal corrections in F , making the averaged vortex interaction isotropic. Hence, the re-entrant transition can be driven by thermal vortex displacements of the order of $\rho \sim \xi_0$. The instability field $H_{\square}(T)$ thus can occur well below the melting line, which in materials of interest here is rather close to H_{c2} .

To find $H_{\square}(T)$ at which $c_s = \partial^2 F / \partial \beta^2|_{\beta=\pi/2} = 0$, we differentiate F of Eq. (6) and obtain:

$$\sum_{mn} \frac{e^{-pg}}{d} \left[(2pmn)^2 + \left(\frac{8m^2 n^2}{d} - g \right) \left(p + \frac{1}{d} \right) \right] = 0. \quad (7)$$

Here, $p = [\pi C + \chi(T)\eta(t, b)/s(b)]b$, $g = m^2 + n^2$, $d = \mu + g + \zeta(b)(m^2 - n^2)^2$, $\mu = 1/2\pi b\kappa^2$. The dimensionless control parameters χ and ζ quantify the amplitude of thermal displacements and the nonlocal corrections:

$$\chi = \frac{16\sqrt{2}\pi^3\lambda_a\lambda_c T}{\phi_0^2\xi_a}, \quad \zeta = \frac{\pi}{2}b\left(\frac{\rho}{\xi}\right)^2. \quad (8)$$

Note that nonlocality enters also the exponent p in Eq. (7) via the parameter η .

For the further analysis, we assume that $\lambda(T) = \lambda(0)/(1 - t^2)^{1/2}$ and $\xi(T) = \xi(0)/(1 - t^2)^{1/2}$, where $t = T/T_c$ (qualitatively, our results do not change if other plausible T dependences are used). Then

$$\chi = \chi_0 t / \sqrt{1 - t^2}, \quad \zeta = \zeta_0 b (1 - t^2), \quad (9)$$

$$\chi_0 = \frac{16\sqrt{2}\pi^3\lambda_a(0)\lambda_b(0)T_c}{\phi_0^2\xi_a(0)}, \quad \zeta_0 = \frac{\pi}{2}\left(\frac{\rho}{\xi_0}\right)^2, \quad (10)$$

In the clean limit $\zeta_0 \sim 1$; with increasing scattering, $\zeta_0(\ell)$ drops fast [10]. For $\text{LuNi}_2\text{B}_2\text{C}$ with $T_c = 16\text{ K}$, $\xi_0 \approx 70\text{ \AA}$, $\lambda_a(0) \approx 10^3\text{ \AA}$, and $\lambda_c(0) \approx 1.2 \times 10^3\text{ \AA}$, we estimate $\chi_0 \approx 6.4 \times 10^{-3} \ll 1$. The smallness of χ_0 indicates that fluctuations contribute little to the thermodynamics of stable VLs [22,18]. As shown below, being crucial on the upper branch of $H_\square(T)$, fluctuations are negligible on the lower branch.

Strictly speaking, $H_\square(T)$ should be calculated *self-consistently* taking into account the effect of fluctuations on the relevant moduli [26]. However, since $\overline{u^2}$ is finite at $H_\square$, we may neglect the thermal softening of c_x and c_ω . Then, $H_\square(T)$ is just a root of Eqs. (7), which we find numerically. The factor η which enters p in Eq. (7) is a much weaker function of t and b than $\chi(t)/s(b)$ (η varies from 1.6 for $c_\omega/c_x = 1$ to 3 for $c_\omega/c_x = 0.1$). For this reason we disregard variation of η , adopting $\eta = 2.7$ for $\text{LuNi}_2\text{B}_2\text{C}$ with $c_\omega/c_x \simeq 0.2$ at $H_\square$ [19].

The results of the numerical solution of Eq. (7) are shown in Fig. 2. It is seen that fluctuations do give rise to the re-entrant square-to-rhombus transition in high fields, in a qualitative agreement with SANS data of Fig. 1. In fact, fluctuations change radically the VL phase diagram in high fields, while weakly affecting the low-field branch of $H_\square$. The difference between $H_\square(T)$ and $H_{c2}(T)$ is significant (except the low- T clean limit) which justifies the use of the London model. As the ratio ρ_0/ξ_0 decreases (e.g., due to nonmagnetic impurities), the region of the square VL on the $H - T$ diagram shrinks. The raise of the lower branch of $H_\square(T)$ has been seen on $\text{Lu}(\text{Co}_x\text{Ni}_{1-x})_2\text{B}_2\text{C}$, for which the mean-free path ℓ was suppressed by the Co doping [13].

It is worth noting that although the calculated curves $H_\square(T, \ell)$ reproduce correctly qualitative features of the SANS data of Fig. 1, actual position of the upper branch is sensitive not only to the accuracy with which we know the elastic moduli and the parameters for their evaluation, but also to the precise value of the empirical cutoff

constant C , see Eq. (1). The information on the actual position of the upper branch of $H_\square(T, \ell)$ is still scarce, and we hope to refine our approximations when the data are available.

Now we comment briefly on the possible effect of the VL transition on the flux pinning. Since the instability of the square VL at $H_\square$ is not accompanied by divergence of $\overline{u^2}$, the critical current density J_c evaluated within the collective pinning theory, should not be sensitive to the VL transition. Indeed, the correlation function of vortex displacements $\langle u(\mathbf{r})u(\mathbf{r}') \rangle$ can be evaluated with the help of Eq. (2) in which T is replaced by $\gamma_p \exp i\mathbf{k}(\mathbf{r} - \mathbf{r}')$, where γ_p is the pinning parameter [22]. At $H_\square$, the squash modulus vanishes, but $\langle u(\mathbf{r})u(\mathbf{r}') \rangle$ remains of the same order as for a triangular London VL, to the accuracy of the weak logarithmic factor $\eta \sim \ln(\xi/\rho b^{1/4}) \sim 1$. Thus, contrary to the claim of Ref. [15], neither the pinning correlation length nor J_c are significantly affected by the squash softening near $H_\square$.

The two-valued $H_\square(T)$ and the re-appearance of the triangular VL at $H \rightarrow H_{c2}$ are generic features which are not limited to nonmagnetic borocarbides. The low- T SANS experiments on antiferromagnetic $\text{TmNi}_2\text{B}_2\text{C}$ have revealed the triangular VL near H_{c2} , which evolves into a square as the field *decreases* [27]. At this stage the effect of antiferromagnetic ordering upon VLs is unclear, but fluctuations could certainly contribute to the re-entrant VL transition in $\text{TmNi}_2\text{B}_2\text{C}$ as they do in $\text{LuNi}_2\text{B}_2\text{C}$. Similar behavior was seen in $\text{YNi}_2\text{B}_2\text{C}$ [28]. Another candidate for studying effects of vortex fluctuation is V_3Si , in which the rhombic VL was observed at $T < 5^\circ\text{K}$ and $H = 10\text{ kOe}$ ($H_\square \simeq 15\text{ kOe}$); as T increases at the fixed field, the rhombic VL evolves toward the hexagonal one as $T \rightarrow T_{c2}(H)$ [4].

In conclusion, we present a model of the structural VL transition at $H_\square(T)$ affected by thermal fluctuations of vortices. We show that the curves $H_\square(T)$ and $H_{c2}(T)$ do not cross, instead $H_\square(T)$ becomes two-valued. The upper branch of $H_\square(T)$ corresponds to a re-entrant transition of the rhombic VL, in accordance with recent SANS observations on $\text{LuNi}_2\text{B}_2\text{C}$.

We are grateful to M. Dodgson and M. Yethiraj for useful discussions. M. Eskildsen kindly provided the data for Fig.1. The work of AG was supported by the NSF MR-SEC (DMR 9214707) and AFOSR. Ames Laboratory is operated for US DOE by the Iowa State University under contract No. W-5405-Eng-82.

- [1] *Anisotropy Effects in Superconductors*, edited by H. Weber, Plenum, New York, 1977; D.K. Christen *et al.*, Phys. Rev. B **21**, 102 (1980).
- [2] P.C. Canfield, *et al.*, Physics Today, **51**, 40 (1998).
- [3] U. Yaron *et al.*, Nature **382**, 236 (1996); M.R. Eskildsen *et al.*, Phys. Rev. Lett. **78**, 1968 (1997); **79**, 487 (1998).
- [4] M. Yethiraj *et al.*, Phys. Rev. Lett. **78**, 4849 (1997); **82**, 5112 (1999).
- [5] D. McK Paul *et al.*, Phys. Rev. Lett. **80**, 1517 (1998).
- [6] Y. De Wilde *et al.*, Phys. Rev. Lett. **78**, 4273 (1997).
- [7] H. Sakata *et al.*, Phys. Rev. Lett. **84**, 1583 (2000).
- [8] V.Ya. Vinnikov *et al.*, Phys. Rev. B **64**, 02445XX (2001).
- [9] U. Klein, J. Low Temp. Phys. **69**, 1 (1987); M. Ichioka, A. Hasegawa, and K. Machida, Phys. Rev. B **59**, 8902 (1999).
- [10] V.G. Kogan *et al.*, Phys. Rev. B **54**, 12386 (1996); **55**, R8693 (1997).
- [11] V.G. Kogan, P. Miranović, and D. McK Paul, in *The Superconducting State in Magnetic Fields*, Series on Directions in Condensed Matter Physics, v. 13; Edited by C.A.R. Sa de Melo, World Scientific, Singapore (1998).
- [12] M. Franz, I. Affleck, and M.H.S. Amin, Phys. Rev. Lett. **79**, 1555 (1997).
- [13] K.O. Cheon *et al.*, Phys. Rev. B **58**, 6463 (1998); P.L. Gammel *et al.*, Phys. Rev. Lett. **82**, 4082 (1999).
- [14] I. Affleck, M. Franz, and M.H.S. Amin, Phys. Rev. B **55**, R704 (1997).
- [15] B. Rosenstein and A. Knigavko, Phys. Rev. Lett. **83**, 844 (1999).
- [16] M.R. Eskildsen *et al.* Phys. Rev. Lett. **86**, 5148 (2001).
- [17] S.B. Dugdale *et al.*, Phys. Rev. Lett. **83**, 4824 (1999).
- [18] E.H. Brandt, Rep. Prog. Phys. **58**, 1465 (1995).
- [19] A detailed discussion of the moduli is given by P. Miranović and V.G. Kogan, cond-mat/0105630.
- [20] V.G. Kogan and L.J. Campbell, Phys. Rev. Lett. **62**, 1552 (1989).
- [21] Since $\text{div} \mathbf{u} = 0$, it is helpful to write $\mathbf{u}$ in terms of a function $A(x, y)$ such that $u_x = \partial_y A$, $u_y = -\partial_x A$.
- [22] G. Blatter *et al.*, Rev. Mod. Phys. **66**, 1125 (1994).
- [23] The modulus $c_\omega = \partial_{\psi\psi}^2 F$ is determined by the energy change due to rotation of the VL over the angle $\psi \rightarrow 0$. Substituting $G_x \rightarrow G_x \cos \psi - G_y \sin \psi$, $G_y \rightarrow G_x \sin \psi + G_y \cos \psi$ into Eq. (6), we obtain in the first order in ρ^2 : $c_\omega = (B^2 \rho^2 / 4\pi \lambda^2) \sum_{mn} (1 - 8m^2 n^2 / g^2) \exp(-pg)$, where $g = m^2 + n^2$, and $p = \pi C b$. For $p \ll 1$, the double sum is $2\sqrt{\pi/p}$, thus $c_\omega = B^2 \rho^2 / 2\lambda^2 \sqrt{p\pi}$.
- [24] E.H. Brandt, J. Low Temp. Phys. **73**, 355 (1988); A. Yaouanc, P.D. de Reotier, and E.H. Brandt, Phys. Rev. B **55**, 11107 (1997).
- [25] R.N. Kleiman *et al.*, Phys. Rev. Lett. **69**, 3120 (1992);

- P.L. Gammel, *et al.*, *ibid.* **72**, 278 (1994).
- [26] P.M. Platzman and H. Fukuyama, Phys. Rev. B **10**, 3150 (1974); D.C. Fisher, *ibid.* **26**, 5009 (1982).
- [27] M.R. Eskildsen *et al.*, Nature **393**, 242 (1998).
- [28] M. Yethiraj and D.K. Christen (unpublished).

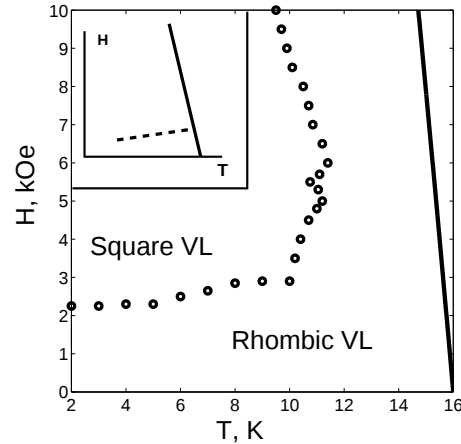


FIG. 1. The transition line $H_\square(T)$ (circles) in $\text{LuNi}_2\text{B}_2\text{C}$ observed by SANS [17]. The inset shows $H_\square(T)$ (dashed line) predicted by the extended GL theory [6] without vortex fluctuations. The solid lines show $H_{c2}(T)$.

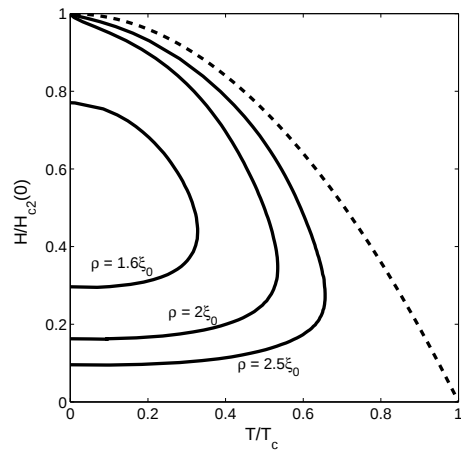


FIG. 2. The transition lines $H_\square(T)$ obtained by numerically solving Eq. (7) for $\chi_0 = 0.0064$, $C = 1$, and a few ratios of ρ/ξ_0 . The dashed line is $H_{c2}(T)$.